arXiv:0909.2207v3 [cond-mat.str-el] 9 Aug 2010

Two-fluid description of magnetic excitations in iron pnictides

Andrew Smerald[1] and Nic Shannon[1]
[1]H. H. Wills Physics Laboratory, University of Bristol, Tyndall Av, BS8–1TL, UK.

(Dated: August 10, 2010)

We present a phenomenological, two-fluid approach to understanding the magnetic excitations in Fe pnictides, in which a paramagnetic fluid with gapless, incoherent particle-hole excitations coexists with an antiferromagnetic fluid with gapped, coherent spin wave excitations. We show that this two-fluid phenomenology provides an excellent description of NMR data for magnetic "122" pnictides, and argue that it finds a natural justification in LSDA and spin density wave calculations. We further use this phenomenology to estimate the maximum renormalization of the ordered moment that can follow from low-energy spin fluctuations in Fe pnictides. We find that this is too small to account for the discrepancy between *ab intio* calculations and neutron scattering measurements.

PACS numbers: 75.10.-b, 75.30.Ds, 67.80.dk

The discovery that, suitably doped, Fe pnictides can superconduct at temperatures greater than 50K[1] has sparked a sudden rush of interest in these materials. Much of this attention has been focused on the magnetism of the parent compounds, which is widely believed to play an essential role in their superconductivity[2–4]. To date, most theoretical approaches to this problem have stressed either the itinerant nature of electrons in Fe pnictides[5–7], or used strong electronic correlation to justify mapping them onto a frustrated local moment model[8–10]. In this paper we embrace the fact that Fe pnictides are both metals and magnets, proposing a simple, phenomenological, two-fluid description of their magnetic excitations. We argue that spin excitations at low energies and temperatures are dominated by the gapless, incoherent particle-hole excitations, characteristic of a metallic paramagnet, while for energies and temperatures comparable with a spin gap Δ_σ, coherent, collective excitations of the magnetic order come into play. It follows naturally from experimental and theoretical determinations of the band structure that these two fluids are essentially independent.

While this two-fluid phenomenology is not dependent on the underlying microscopic model, it finds a natural justification in recent spin density wave calculations, which assign metallic and magnetic electrons to different sheets of the Fermi surface[11–15]. It is also consistent with the band structure measured by photoemission studies and calculated by LSDA[7]. Here we show that it provides an excellent description of NMR experiments on Fe pnictides with 122 structure[16,17]. We also critically re-examine attempts to understand magnetism in Fe pnictides in terms of frustrated local-moment models[8–10]. While a two-fluid phenomenolgy does not rule out frustration *per se*, we find that quantum fluctuations *cannot* account for the observed reduction of the ordered moment relative to LDA calculations[5,6].

Both the magnetic and metallic properties of Fe pnictides originate in outer-shell Fe 3d-electrons. Band structure calculations[5,6,18], supported by photoemission[19,20] and quantum oscillation[21,22] experiments, suggest that these hybridize with As 4p orbitals to form a Fermi surface with two electron-like and three hole-like pockets, when viewed in a "natural" unfolded Brillouin zone based on Fe sites. The fact that magnetic Fe pnictides are metals implies that some part of this complex Fermi surface remains gapless, and will support incoherent particle-hole excitations with vanishing energy. We treat this as the first of our fluids, characterized simply by an average density of states at the Fermi energy, n_0, which can be estimated from heat capacity measurements.

Neutron scattering experiments[23–26], meanwhile, reveal a commensurate, collinear, antiferromagnetic (AF) ground state with ordering vector $\mathbf{k}^* = (\pi, 0, \pi)$, and ordered Fe moment $m_S \approx 1\mu_B$, much smaller than predicted by *ab initio* calculations[5,6]. A single branch of spin wave excitations with dispersion,

$$\omega_{\mathbf{k}'} = \sqrt{\Delta_\sigma^2 + (\mathbf{v}.\mathbf{k}')^2}, \tag{1}$$

is found above a gap $\Delta_\sigma \approx 10meV$ at the ordering vector $\mathbf{k}' = \mathbf{k} - \mathbf{k}^* = (0, 0, 0)$. Spin wave velocities $\mathbf{v} = (v_x, v_y, v_z)$ are anisotropic, with $v_x \approx v_y \gg v_z$. The collective excitations of this magnetic order form our second fluid, and, following [27], we characterize them using a quantum non-linear sigma model,

$$\begin{aligned} S \;=\; \frac{1}{2abc}\int d\mathbf{x}dt \left[\hbar^2\chi_\perp(\partial_t\mathbf{n})^2 - \rho_x(\partial_x\mathbf{n})^2 - \rho_y(\partial_y\mathbf{n})^2 \right. \\ \left. -\rho_z(\partial_z\mathbf{n})^2 + \chi_\perp\Delta_\sigma^2 n_x^2\right], \end{aligned} \tag{2}$$

where $\chi_\perp$ is the static perpendicular susceptibility, ρ_x, ρ_y and ρ_z are spin stiffness' along the major crystal axes a, b, c, and Δ_σ^2 is an easy axis anisotropy.

For $\Delta_\sigma \to 0$, this action describes the long-wavelength Goldstone modes, which follow from the symmetry of the magnetic order. As such, it can be derived from *any* microscopic model that respects these symmetries, whether localized or itinerant. For finite anisotropy $\Delta_\sigma > 0$, Eq. (2) predicts a gapped, two-fold degenerate cone of spin wave excitations with exactly the form Eq. (1), where $v_\alpha = \sqrt{\rho_\alpha/\chi_\perp}$. Within a spin density wave picture, Eq. (2) should remain valid up to an energy scale of the spin-density wave gap, estimated to be

	$\delta m_S(T)\ (\mu_B)$
$T \ll \Delta_\sigma$	$\frac{m_0(abc)\sqrt{\Delta_\sigma}}{8\chi_\perp \bar{v}_s^3}\left(\frac{2k_BT}{\pi}\right)^{\frac{3}{2}}\mathrm{e}^{-\frac{\Delta_\sigma}{k_BT}} = M_{\mathsf{LT}}T^{\frac{3}{2}}\mathrm{e}^{-\frac{\Delta_\sigma}{k_BT}}$
$T \gg \Delta_\sigma$	$\frac{m_0(abc)}{12\chi_\perp \bar{v}_s^3}(k_BT)^2 = M_{\mathsf{HT}}T^2$

TABLE I: Leading temperature correction to the ordered moment ($m_s = m_0 - \delta m_S - \delta m_S(T)$) from spin wave excitations. The form of corrections depends only on the gap, Δ_σ. The prefactor is determined by the geometric mean spin wave velocities, $\bar{v}_s^3 = v_x v_y v_z$ $[(meV\mathring{A})^3]$, bare moment m_0 $[\mu_B]$, transverse susceptibility $\chi_\perp$ $[meV^{-1}]$ and Fe-Fe lattice parameters a, b, c $[\mathring{A}]$.

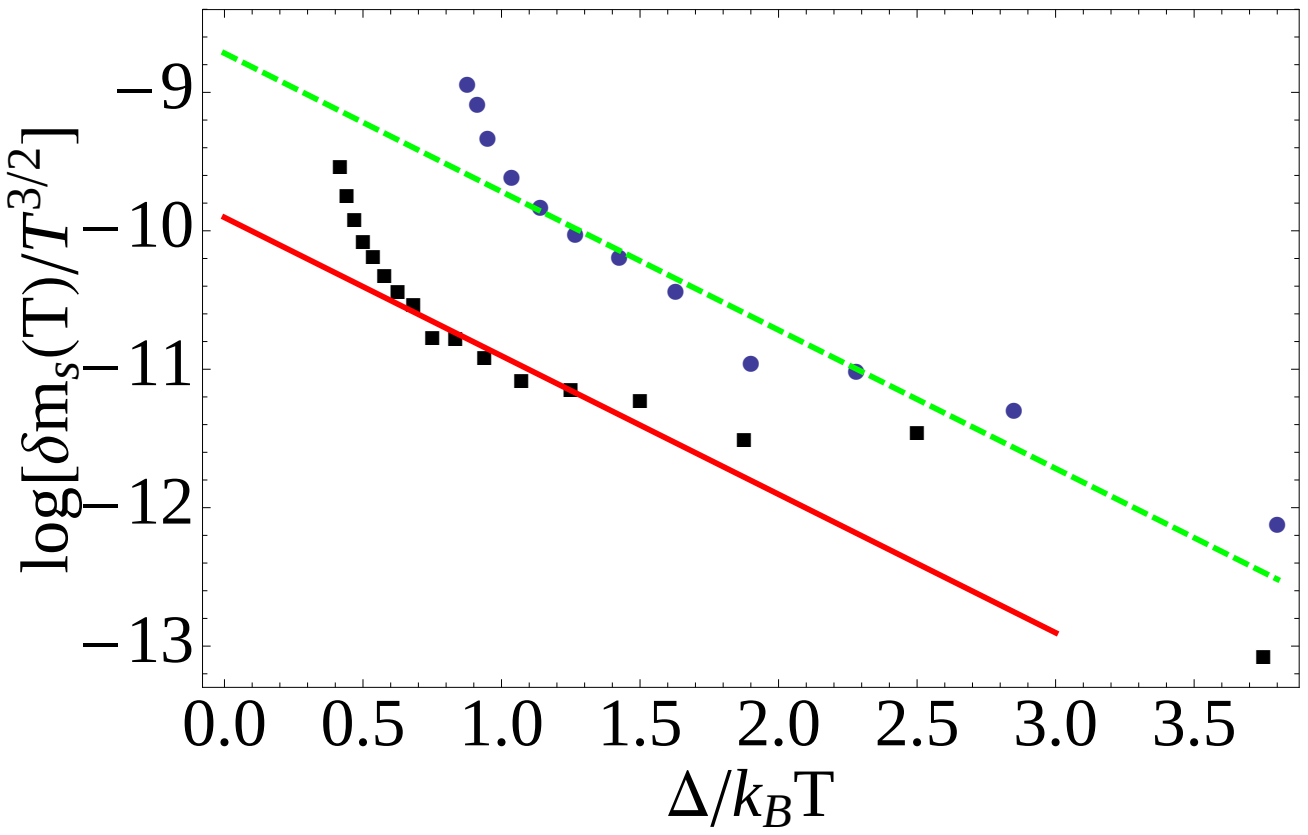

FIG. 1: (Color online). Temperature dependence of the ordered moment $\delta m_S(T)$ as determined by NMR measurements on $BaFe_2As_2$[16] (blue circles) and $SrFe_2As_2$[17] (black squares). Data is plotted as $\log\left[\delta m_S(T)/T^{\frac{3}{2}}\right]$ vs Δ_σ/k_BT, where the values of $\Delta_{Ba} = 114K$ and $\Delta_{Sr} = 75K$ are taken from inelastic neutron scattering experiments[23,26]. Straight lines show the expected form of corrections at low temperatures. The intercept gives the prefactors $M_{\mathsf{LT}}^{Ba} \approx 1.6 \times 10^{-4}\ \mu_B K^{-\frac{3}{2}}$ and $M_{\mathsf{LT}}^{Sr} \approx 5 \times 10^{-5}\ \mu_B K^{-\frac{3}{2}}$

$\Delta_{\mathsf{SDW}} \approx 31meV$ for LaFeAsO[15]. For the specific case of $CaFe_2As_2$, it breaks down at energies of approximately 150meV, where the spin wave branch is seen to enter a continuum of excitations[24].

Our final approximation is to ignore all coupling between these two fluids. This appears justified for two reasons. Firstly neutron scattering studies[24–26] observe sharp cones of low energy magnetic excitations with no evidence of the damping that would be expected if the spin waves could scatter from the metallic fluid. Secondly LSDA calculations[7], photoemission studies[7] and SDW theory[13–15] show no evidence, in the ordered state, for a nested pair of Fermi surfaces with spanning vector $(\pi, 0)$. Hence, within a band picture, there are no available particle-hole states close to the ordering vector for the spin waves to decay into.

A simple test of our phenomenology is provided by the temperature dependence of the ordered moment $\delta m_S(T)$. Within the two-fluid picture, this is controlled by the thermal excitation of spin waves, as described by Eq. (2). Table I summarises our predictions. At temperatures relevant to experiment, the spin gap dominates, and in Fig. 1 we compare the predicted form of $\delta m_S(T)$ with the low temperature ordered moment, as measured by NMR experiments on $BaFe_2As_2$[16] and $SrFe_2As_2$[17]. We have checked that similar fits can be made for $\delta m_S(T)$ obtained from μSR for LaOFeAs[28,29] and $SrFe_2As_2$[30].

NMR experiments also probe spin excitations through the nuclear spin lattice relaxation rate, $1/T_1$. This has been measured for As nuclei in $BaFe_2As_2$[16] and $SrFe_2As_2$[17]. For hyperfine interactions, the relaxation rate is given by[31,32],

$$\frac{1}{T_1} \approx \frac{\gamma_N^2}{2} k_B T \lim_{\omega_0 \to 0} \frac{1}{N} \sum_{\mathbf{q}} |\mathcal{A}_{\mathbf{q}}|^2 \frac{\chi''(\omega_0, \mathbf{q})}{\hbar\omega_0}, \tag{3}$$

where γ_N is the gyromagnetic ratio of the nucleus in question and ω_0 is the nuclear excitation energy. Both fluids contribute to $1/T_1$, but at low temperatures the leading contribution will come from gapless particle-hole pairs within the paramagnetic fluid. We assume that the hyperfine interaction is roughly constant, $|\mathcal{A}_{\mathbf{q}}|^2 \approx |\mathcal{A}_0|^2$ $[(T/\mu_B)^2]$, over the relevant sheet of the Fermi surface, in which case the contribution to $1/T_1$ will be linear in T [32],

$$1/T_1^{\mathsf{inc.}} \approx \frac{1}{4}\pi\hbar\gamma_N^2|\mathcal{A}_0|^2 g_L^2 (abc)^2 n_0^2 k_B T = C_{inc} T, \tag{4}$$

where g_L is the Lande g-factor and we use units where $\mu_B = 1$.

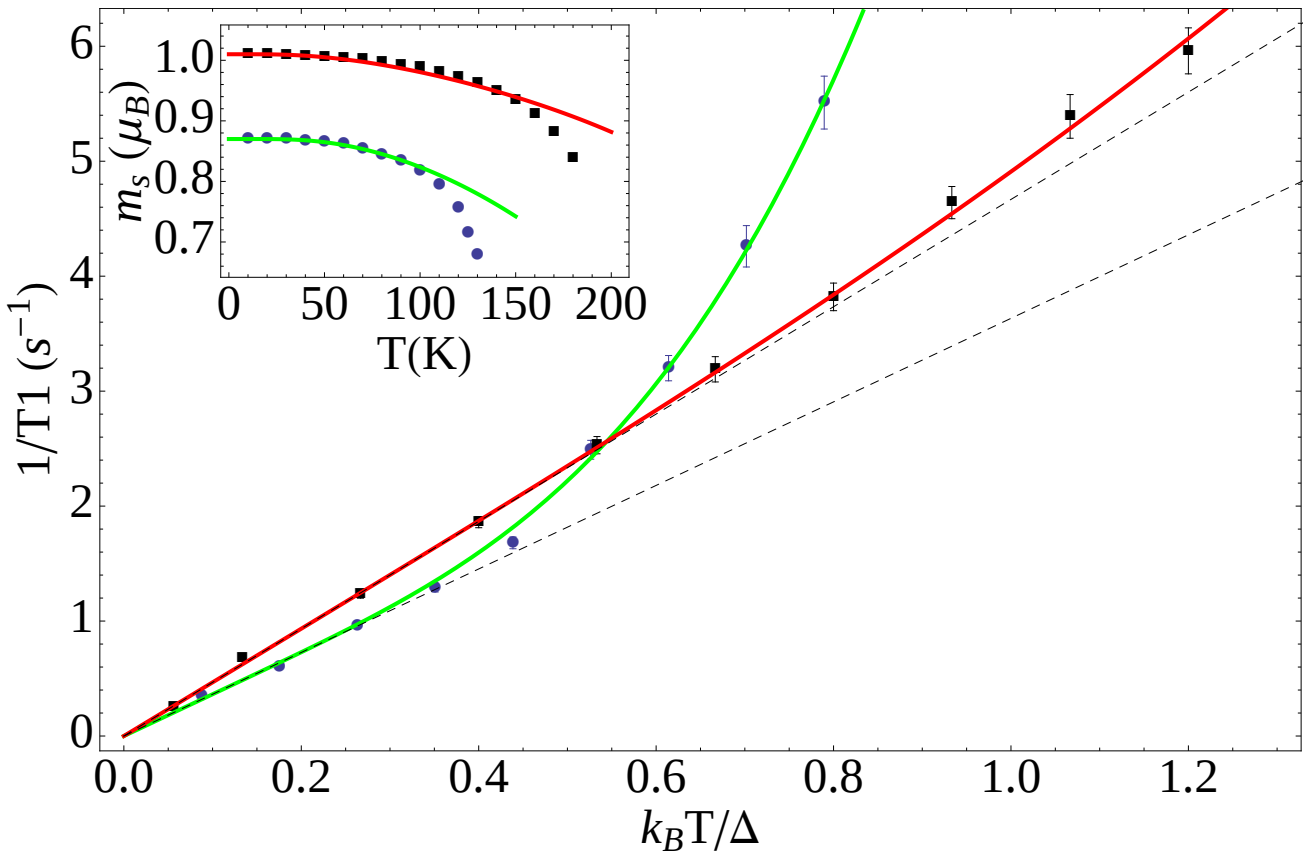

FIG. 2: (Color online). Simultaneous fits to nuclear relaxation rate T_1^{-1} and sublattice magnetsation $m_S(T)$ for $BaFe_2As_2$[16] (blue dots) and $SrFe_2As_2$[17] (black squares). The dashed lines show the contribution of incoherent particle-hole pairs Eq. (4); the full lines show the combined fit including the contribution of coherent, thermally-activated spin waves Eq. (6). The gap values $\Delta_{Ba} = 114K$ and $\Delta_{Sr} = 75K$ are taken from inelastic neutron scattering experiments[23,26]. Insets show simultaneous fits to the sublattice magnetisation, m_S. The prefactors are determined to be, $C_{inc}^{Ba} \approx 0.032\ s^{-1}K^{-1}$, $C_{coh}^{Ba} \approx 7.5\ s^{-1}$, $C_{inc}^{Sr} \approx 0.062\ s^{-1}K^{-1}$ and $C_{coh}^{Sr} \approx 0.28\ s^{-1}$.

At higher temperatures, the Raman scattering of thermally excited spin waves also plays a role in nuclear spin

	$M^{Ba}_{\mathsf{LT}}[\mu_B K^{-\frac{3}{2}}]$	$C^{Ba}_{inc}[(sK)^{-1}]$	$C^{Ba}_{coh}[s^{-1}]$
Fit	1.6×10^{-4}	0.032	7.5
Estimate	$(0.15 - 2.2) \times 10^{-4}$	~ 0.015	$0.14 - 33$

TABLE II: Quantitative analysis of $\delta m_s(T)$ and T_1^{-1} in $\mathrm{BaFe_2As_2}$. We determine the prefactors M^{Ba}_{LT} (Table I), C^{Ba}_{inc} (Eq. 4), and C^{Ba}_{coh} (Eq. 6) by fitting NMR experiments (cf. Figs. 1, 2) and compare these with the quantitative estimates which follow from known values of the hyperfine interactions $\mathcal{A}_0 \sim 1.88\ T/\mu_B$ and $\mathcal{B}_{ac} = 0.43\ T/\mu_B$[16], spin-wave velocities $95 < \bar{v}_s < 228\ meV\mathring{A}$ [26], spin-gap $\Delta_\sigma = 9.8(4)\ meV$ [26], ordered moment $m_0 = 0.87\ \mu_B$[40], perpendicular susceptibility $\chi_\perp = 10^{-4}\ emu/mol$ [41], lattice constants $[a, b, c] = [2.80, 2.79, 6.47]\ \mathring{A}$ [40], and density of states $n_0 = 5.8 \times 10^{24}\ J^{-1}m^{-3}$ [42].

relaxation. NMR probes the longitudinal susceptibility $\chi''_\parallel(\omega_0, \mathbf{q})$, which can be calculated directly from Eq. (2). We consider relaxation due to hyperfine coupling of the As nucleus to a four site plaquette of nearest neighbour Fe sites, in the same spirit as [33]. For external fields applied in the FeAs plane we calculate the form factor,

$$|\mathcal{A}_\mathbf{q}|^2 = 4\mathcal{B}^2_{ac}\left(1 - \cos q_x + \cos q_y - \cos q_x \cos q_y\right), \quad (5)$$

where $\mathcal{B}_{ac} = 0.43\ T/\mu_B$ [16] is the hyperfine matrix element relevant for Raman relaxation processes. The imaginary part of the susceptibility is very sharply peaked for scattering by the ordering vector, and hence we approximate the slowly varying form factor by $|\mathcal{A}_\mathbf{q}|^2 = 16\mathcal{B}^2_{ac}$, and sum over a small region surrounding $\mathbf{q} = (\pi, 0, \pi)$. We find,

$$\frac{1}{T_1^{\mathsf{coh.}}} \approx \frac{2\mathcal{B}^2_{ac} m_0^2 \hbar (abc)^2 \gamma_N^2 \Delta_\sigma^3}{\pi^3 \chi_\perp^2 \bar{v}_s^6} \Phi\left[\frac{k_B T}{\Delta_\sigma}\right] = C_{coh}\Phi\left[\frac{k_B T}{\Delta_\sigma}\right] (6)$$

where $\Phi(x) = x^2 \mathrm{Li}_1(e^{-1/x}) + x^3 \mathrm{Li}_2(e^{-1/x})$, and $\mathrm{Li}_n(z) = \sum_{k=0}^\infty z^k/k^n$ is the nth polylogarithm of z.

We are now in a position to compare directly with experiment, and, in Fig. 2, we show the results of simultaneous fits to NMR data for $\delta m_S(T)$ and $1/T_1$ in $\mathrm{BaFe_2As_2}$[16] and $\mathrm{SrFe_2As_2}$[17]. We treat the total relaxation rate as the sum of the contributions of the two fluids, Eq. (4) and Eq. (6) and fit the prefactors M^{Ba}_{LT} (Table I), C^{Ba}_{inc} (Eq. 4), and C^{Ba}_{coh} (Eq. 6), using the experimental value $\Delta_{Ba} = 114K$[26] for the gap. The agreement is excellent. It is also possible to make independent, *quantitative* estimates of these fit parameters by substituting known values of the model parameters directly into the relevant equations. In Table II we show that these two approaches are quantitatively consistent for $\mathrm{BaFe_2As_2}$[43]

One of the important issues in Fe pnictide magnetism has been the size of the ordered moment m_S. Fe and its oxides typically show a large ordered moment at low temperatures. First principles calculations for magnetic Fe pnictides suggest that $m_S \approx 1.5$–$1.7\mu_B$[5,6]. The moment measured by neutron scattering, in contrast, ranges from $0.25\mu_B$ (NdFeAsO)[35] to $1\mu_B$ ($\mathrm{SrFe_2As_2}$)[36]. The AF "stripe" order found in Fe pnictides has also been observed in quasi-two dimensional insulating oxides with frustrated exchange interactions, where the ordered moment is strongly renormalized by quantum fluctuations[34]. By analogy, it has been suggested that magnetic excitations in Fe pnictides can also be understood in terms of a frustrated local-moment model,

$$\mathcal{H} = J_{1x} \sum_{\langle ij \rangle_{1x}} \mathsf{S}_i.\mathsf{S}_j + J_{1y} \sum_{\langle ij \rangle_{1y}} \mathsf{S}_i.\mathsf{S}_j + J_{1z} \sum_{\langle ij \rangle_{1z}} \mathsf{S}_i.\mathsf{S}_j$$
$$+ J_2 \sum_{\langle ij \rangle_2} \mathsf{S}_i.\mathsf{S}_j - K_{xy} \sum_i \left((\mathsf{S}_i^x)^2 - (\mathsf{S}_i^y)^2\right) + K_z \sum_i (\mathsf{S}_i^z)^2 (7)$$

where $\langle ij \rangle_{1\alpha}$ counts first-neighbor bonds in the α-direction, $\langle ij \rangle_2$ second-neighbour bonds in the x-y plane, and K_{xy} is a single-ion anisotropy. It is interesting, therefore, to ask what constraints our two-fluid phenomenology places on this effective local-moment picture ?

A telling, and direct, comparison can be made in the context of the ordered moment. At a mean field level, the collinear "stripe" phase of the square-lattice J_1–J_2 Heisenberg model becomes unstable for $J_2 < |J_1|/2$ [37]. Approaching this transition, quantum corrections to the ordered moment diverge, as illustrated in Fig. 3. For AF J_1, the dominant correction to m_S comes from spin waves near the ordering vector. These are described by Eq. (2) with $v_z = \Delta_\sigma = 0$, and we find,

$$\delta m_S = \frac{m_0}{2\chi_\perp} \frac{a^2}{(2\pi)^2} \int_{|\mathbf{k}|<\Lambda} \frac{d\mathbf{k}}{\omega_\mathbf{k}} = \frac{m_0 a^2 \Lambda}{4\pi^2 \chi_\perp v_x} \mathsf{K}_1(\kappa), \quad (8)$$

where Λ is a momentum cut-off reflecting the size of the spin-wave "cone", K_1 is a complete elliptic integral of the first kind, and $\kappa = \sqrt{1 - (v_y/v_x)^2}$. At the limit of the $(\pi, 0)$ AF phase, $v_y \to 0$, and δm_S diverges logarithmically[38]. The contribution of spin waves at higher energies must be determined separately, but for present purposes can be approximated by a constant offset $\approx 0.1\mu_B$.

At first sight, fine-tuning a J_1–J_2 model into a region with $v_y \ll v_x$ offers the possibility of achieving any desired renormalization of the ordered moment, m_S, cf.[8–10]. The same would hold of any itinerant electron model which could be mapped onto Eq. (2). However, neutron scattering results for Fe pnictides suggest that $v_y \approx v_x$ [25]. Moreover, they clearly show a spin gap Δ_σ, and out-of-plane dispersion v_z, both of which act to cut-off the divergence in δm_S.

For a gapped, three-dimensional dispersion with $v_y > \sqrt{v_x v_z (\Lambda/\pi)^3}$, Eq. (2) predicts

$$\delta m_S \approx \frac{m_0 abc \Delta_\sigma}{8\pi^2 \chi_\perp \bar{v}_s^3} \left(\Lambda \bar{v}_s \sqrt{1 + \frac{\Lambda^2 \bar{v}_s^2}{\Delta_\sigma^2}} - \Delta_\sigma \operatorname{arcsinh}\left[\frac{\Lambda \bar{v}_s}{\Delta_\sigma}\right]\right) (9)$$

For parameters relevant to $\mathrm{BaFe_2As_2}$, with $\Lambda \approx 0.2\pi/a$ [26], this implies $\delta m_S \approx 0.13\mu_B$, a value too small to explain the gulf between *ab intio* calculations and experiment, although comparable with the smaller discrepancy with model based SDW theory[12].

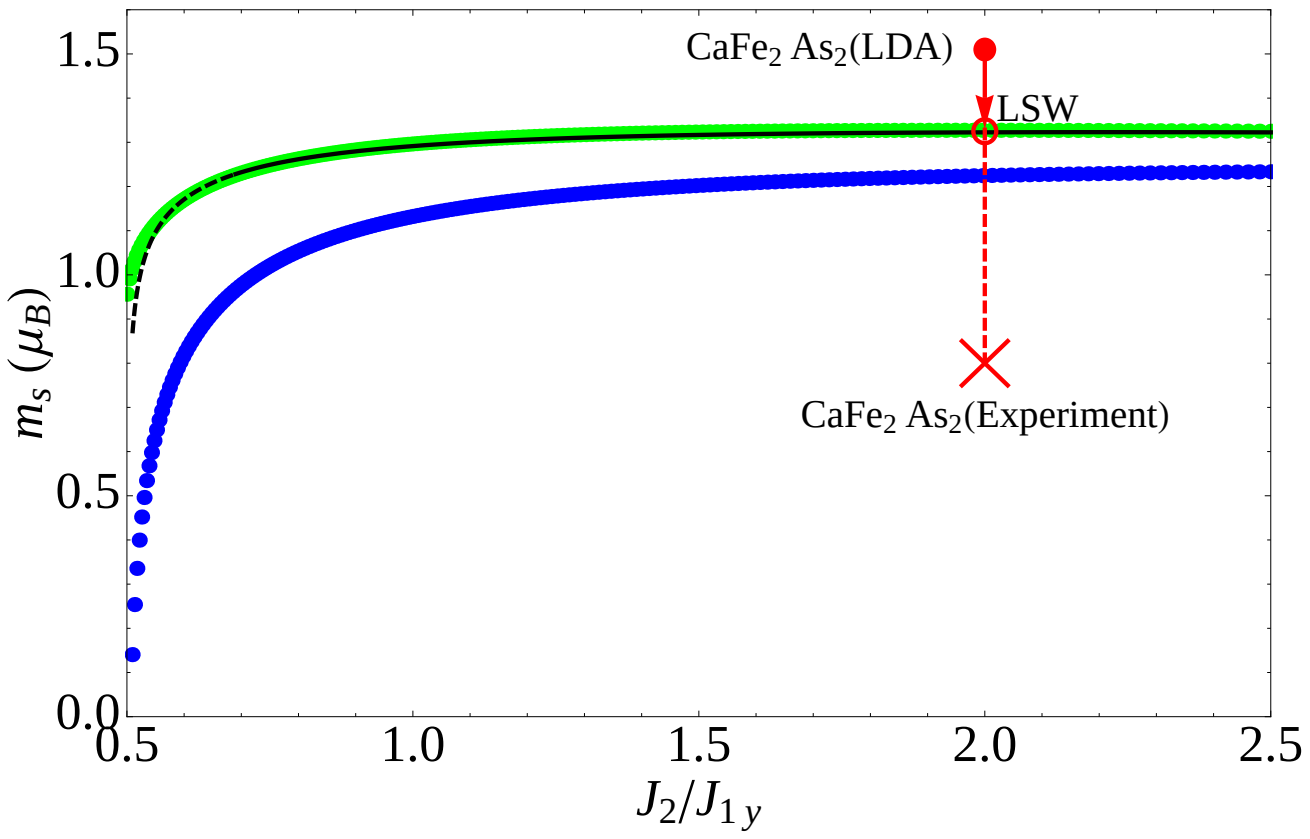

FIG. 3: (Color online). Zero temperature sublattice magnetisation m_S calculated within linear spin wave theory (LSW) for the 3D Heisenberg model Eq. (7) (upper, green dots) and the square-lattice J_1–J_2 model (lower, blue dots), as a function of J_2. Remaining parameters for Eq. 7 are taken from experiment on CaFe$_2$As$_2$ [25]. We use $m_0 = 1.51$, $J_{1x} = 30meV$, $J_{1y} = 15meV$, $J_{1z} = 4.5meV$ and $K_{xy} = K_z = 0.12meV$. The solid black line shows the sigma-model prediction Eq. (9). The divergent correction seen in the 2D J_1–J_2 model for $J_2/J_1 \to^+ 1/2$ is cut off by the gap spin Δ_σ and 3D spin-wave dispersion.

In the highly frustrated region $v_y \to 0$, Eq. (9) provides a finite bound, $\delta m_S \lesssim m_0\Lambda^3 abc/(16\pi^2\chi_\perp\Delta_\sigma)$, on the maximum correction to the ordered moment from low-energy spin waves. To illustrate how this works, in Fig. 3 we compare the predictions of the nonlinear sigma model, Eq. (2), and the Heisenberg model, Eq. (7), for the sublattice magnetization, m_S, as a function of J_2 — and thereby v_y. Remaining parameters for Eq. (7) are taken from experiments on CaFe$_2$As$_2$ [25]. Following LDA calculation[5], we set the bare moment $m_0 = 1.51\mu_B$. A constant offset $\delta m_S = -0.3\mu_B$ is added to Eq. (9) to correct for high energy spin waves. The agreement is excellent for a wide range of J_2. Even at the maximally frustrated point, the correction $\delta m_S \approx 0.5\mu_B$ is smaller than the $\delta m_S \approx 0.7\mu_B$ needed to explain the discrepancy with experiment. We anticipate that this conclusion will hold for *any* spin model with realistic parameters[39], and conclude that the failure of LDA to accurately describe the size of the ordered moment lies in high-energy electronic correlation effects, not the zero point motion of low-energy spin waves.

In conclusion, magnetic excitations in Fe pnictides are well-described by a simple two-fluid phenomenology in which gapped, three-dimensional spin waves co-exist with gapless, but incoherent particle-hole pairs. These two fluids can be treated as independent. This phenomenology is blind as to microscopic details of the real materials, but seems to fit naturally with spin-density wave calculations which assign magnetism and metallicity to different, weakly coupled, sheets of the Fermi surface.

Acknowledgments. We are pleased to acknowledge helpful discussions with Andrey Chubukov, Amalia Coldea, Dima Efremov, Ilya Eremin, Cristoph Geibel, Stephen Hayden, Frederic Mila, Kenya Ohgushi, Toby Perring, Masashi Takigawa and Alexander Yaresko. We endebted to Yasutomo Uemura for important conversations at an early stage of this work. This work was supported under EPSRC grants EP/C539974/1 and EP/G031460/1

---

[1] Y. Kamihara *et al.* J. Phys. Soc. Jpn., **130**, 3296 (2008)
[2] C. Lester *et al.* Phys. Rev. B **79**, 144523 (2009)
[3] Y. Uemura, Nat. Matt. **8**, 253 (2010)
[4] For an alternative view, see J. Wilson, J. Phys.: Condens. Matter **22** 203201 (2010).
[5] M. J. Han *et al.*, Phys. Rev. Lett. **102**, 107003 (2009)
[6] A. N. Yaresko *et al.*, Phys. Rev. B **79**, 144421 (2009)
[7] M. Yi *et al.*, Phys. Rev. B **80**, 174510 (2009)
[8] Q. Si *et al.*, Phys. Rev. Lett. **101**, 076401 (2008)
[9] D.-X. Yao *et al.* , Phys. Rev. B **78**, 052507 (2008)
[10] G. S. Uhrig *et al.*, Phys. Rev. B **79**, 092416 (2009)
[11] M. M. Korshunov and I. Eremin, Phys. Rev. B **79**, 140509(R) (2008)
[12] H.-H. Klauss *et al.*, Phys. Rev. Lett. **101**, 077005 (2008)
[13] Ying Ran *et al.*, Phys. Rev. B **79**, 014505 (2009)
[14] I. Eremin and A. V. Chubukov, Phys. Rev. B **81**, 024511(2010)
[15] J. Knolle *et al.*, Phys. Rev. B **81**, 140506 (2010)
[16] K. Kitagawa *et al.*, J. Phys. Soc. Jpn. **77**, 114709 (2008)
[17] K. Kitagawa *et al.*, J. Phys. Soc. Jpn. **78**, 063706 (2009)
[18] D. J. Singh and M.-H. Du, Phys. Rev. Lett. **100**, 237003 (2008)
[19] D. V. Evtushinsky *et al.*, Phys. Rev. B **79**, 054517 (2009)
[20] C. Liu *et al.* Phys. Rev. Lett. **101**, 177005 (2008)
[21] A. I. Coldea *et al.*, Phys. Rev. Lett. **101**, 216402 (2008)
[22] J. Analytis *et al.*, Phys. Rev. Lett. **103**, 076401 (2009)
[23] J. Zhao *et al.*, Phys. Rev. Lett. **101**, 167203 (2008)
[24] J. Zhao *et al.*, Nature Physics **5** 555 (2009)
[25] S. O. Diallo *et al.*, Phys. Rev. Lett. **102**,187206 (2009)
[26] K. Matan *et al.*, Phys. Rev. B **79**, 054526 (2009)
[27] A. Ong *et al.*, Phys. Rev. B **80**, 014514 (2009)
[28] J. P. Carlo *et al.* , Phys. Rev. Lett. **102**, 087001 (2009)
[29] Y. J. Uemura, Physica B **404**, 3195 (2009)
[30] A. Jesche *et al.*, Phys. Rev. B **78**, 180504(R), (2008)
[31] T. Moriya, Prog. Theor. Phys. **16**, 641 (1956)
[32] T. Moriya, J. Phys. Soc. Japan **18**, 4 (1963)
[33] F. Mila and T. M. Rice, Phys. Rev. B **40**, 11382 (1989)
[34] M. Skoulatos *et al.*, Eur. Phys. Lett. **88**, 57005 (2009)
[35] K. Kaneko *et al.*, Phys. Rev. B **78**, 212502 (2008)
[36] Y. Chen *et al.*, Phys. Rev. B **78**, 064515(2008)
[37] N. Shannon *et al.* Eur. Phys. J B **38**, 599 (2004)
[38] P. Chandra *et al.*, Phys. Rev. B **38**, 9335(R) (1988)
[39] B. Schmidt *et al.*, Phys. Rev. B **81**, 165101 (2010).
[40] Q. Huang *et al.*, Phys. Rev. Lett. **101**, 257003 (2008)
[41] F. Ning *et al.*, J. Phys. Soc. Jpn. **78**, 013711 (2009)
[42] M. Rotter *et al.*, Phys. Rev. B **78**, 020503 (2008)
[43] Uncertainty in the model parameters for SrFe$_2$As$_2$ are currently too great for a quantitative comparison.